




Dept. of Mech. Eng.
CUET

Published Online March 2019 (<http://www.cuet.ac.bd/merj/index.html>)

Mechanical Engineering Research Journal

Vol. 11, pp. 1–6, 2018



ISSN: 1990-5491

EFFECT OF POISSON'S RATIO ON THE INTERFACIAL-STRESS STATE OF BILAYER COMPOSITES VIA FINITE DIFFERENCE METHOD

M. Y. Bhuiyan^{1*}, A. R. Chowdhury² and M. A. S. Akanda²

¹Department of Mechanical Engineering, University of South Carolina, Columbia 29208, USA

²Department of Mechanical Engineering, Bangladesh University of Engineering and Technology, Dhaka-1000, Bangladesh

Abstract: The bilayer composites are very important fundamental structures of the single walled carbon nanotubes (SWNTs), layered graphene structures, micro-mechanics study of composites, multi-layered hybrid materials. The interfacial-stress state highly affects the design of such materials. In this paper, a numerical finite difference method (FDM) was used to study the effect of Poisson's ratio on the interfacial-stresses of a bilayer composite material. A displacement potential function was used to formulate the governing equations, displacements, and stresses. Appropriate finite difference schemes were used for the discretization of the bi-harmonic governing equation and the associated boundary conditions. Proper treatment of the boundary conditions was performed at the interface and the corner points of the bilayer. It was found that the Poisson's ratio had a significant effect on the stress-state at the interface as well as inside the materials. Non-linear behavior and a sudden jump in the stresses was observed in the materials.

Keywords: FDM, bi-harmonic governing equations, displacement potential function, micro-mechanics, composites, bi-layer composites.

NOMENCLATURE

σ = Stress (Pa)
 u, v = Displacement (m)
 ψ = Displacement potential function (m^3)
 E = Young's modulus of elasticity (Pa)
 μ = Poisson's ratio (dimensionless)

1. INTRODUCTION

Now-a-days composite is a very common word because of its multipurpose application in many industries such as aerospace, automotive, marine, construction etc. [1–3]. The word “composite” means ‘consisting of two or more distinct parts’. Composites are formed by laying up different materials to form an overall structure that is better than the individual components [4–6]. The constituent materials have significantly different physical or chemical properties than the combined layers. The individual layer remains separate and distinct within

its domain. In a bilayer composite, there are two materials bonded together having different mechanical properties.

The bilayer composites, such as metal-metal, steel-polymer, concrete-steel etc., having different mechanical properties layer by layer are widely used for modern structures [7–9]. They are widely used for single walled carbon nanotubes (SWNTs) and layered graphene structures. In addition, the study of bilayer composite could provide fundamentals of the micro-mechanics study of composites, multi-layered hybrid materials [10–12]. Therefore, knowing the behavior of bilayer composites under the action of mechanical loading is important for designing the structures. Several methodologies could be used for the solution of a same problem. These methodologies can be classified into three general categories: Experimental, analytical and numerical methods. Usually, the experimental method is used for to study the actual behavior and the experimental results are often compared with the numerical simulation results. However, it requires special equipment, testing facilities and thus, often very costly. Analytical solution of a problem is very fast and impressive but sometimes impossible for complex boundary

*Corresponding author: Email: yeasin85@gmail.com

conditions and geometries [13]. The numerical methods have become popular and the ultimate choice of the researchers in the last few decades. Invention and rapid improvement of the computing machine, i.e. sophisticated high-performance computers have accelerated the popularity of the numerical methods.

Stress analysis of bilayer composite requires the solution of partial differential equations. There are various numerical methods available for the solution of partial differential equations. Among them, the most popular methods are Finite Element Method (FEM) and Finite Difference Method (FDM). Finite difference method is an ideal numerical approach for solving partial differential equations. The difference equations that are used to model governing equations in FDM are very simple to code and the global coefficient matrix produced by FDM is a banded structure and is very effective to obtain good solution. In spite of these characteristics, now-a-days, finite difference method has been used in most of the engineering applications. Finite element method (FEM) is also a popular numerical method. The finite element modeling can be efficiently performed with complex boundary shapes. Displacement potential based FDM has been used for many applications [14–16]. FEM could produce reliable result within the body of the structure. However, at certain boundary of the body, FEM may underestimate the critical stress value. In fact, Dow et al. [17] obtained higher accuracy for the stress state at the boundary by using FDM as compared to the FEM. Hossain *et al.* [18] showed that an efficient approach based on finite difference method for efficient computational effort. It has been shown that the computation time is faster than the other methods. In general, the critical stresses happened in the complex boundaries such as corners, interfaces. The interface-stress is significantly affected by the material properties. The interface-stress is very critical in designing the composite material system [19,20].

The present work deals with the study of the Poisson's ratio effect on the interface-stress state of a bilayer composite. Finite difference method has been used to discretize the governing equations and the boundary conditions. Appropriate finite difference scheme and special treatment of the interface boundaries has been performed. It was found that the Poisson's ratio has a significant effect on the stress-state at the interface as well as inside the materials. Non-linear behavior and a sudden jump in the stresses has been observed in the materials.

2. PROBLEM DEFINITION, THEORY AND NUMERICAL MODELING

2.1 Problem Definition and Theory

Stress state analysis in a generic material body is usually a three-dimensional problem. Fortunately, the most practical problems are often found to conform with the plane stress or plane strain states, hence, the stress analysis of 3-D bodies can easily be treated as a 2-D problem [21–24]. Let us consider a bilayer composite as shown in Fig. 1(a) with two-dimensional geometry. Each layer is isotropic within its domain but has

different material properties from each other. The modulus of elasticity of top and bottom layers are E_1 and E_2 , respectively. The Poisson's ratios of top and bottom layers are μ_1 and μ_2 , respectively. The numerical results developed in this paper are generic and valid for both plane stress and plane strain cases of the composite. Only difference is - for plane stress, the third dimension of the bilayer can be considered as very thin having no stress components in the thickness direction and for plane strain, the third dimension of the bilayer can be considered as very thick having no strain components in the thickness direction. The bilayer is subjected to a uniform stress on the right side and fixed on the left side, hence, making it a mixed boundary value problem. The boundary conditions of the present problem is illustrated in Fig. 1b.

The generic governing equation for the mixed boundary value problem is a bi-harmonic equation [25], i.e.

$$\frac{\partial^4 \psi}{\partial x^4} + 2 \frac{\partial^4 \psi}{\partial x^2 \partial y^2} + \frac{\partial^4 \psi}{\partial y^4} = 0 \quad (1)$$

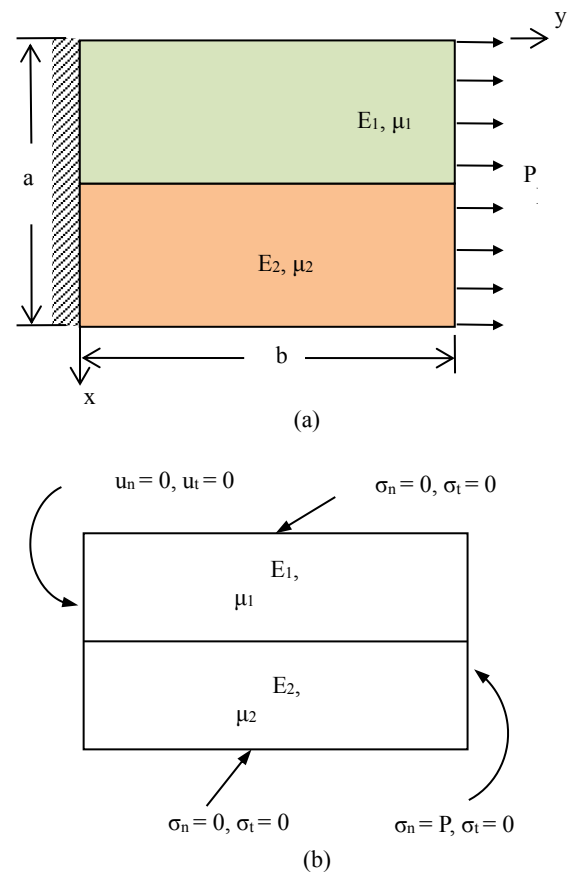


Fig. 1 (a) A schematic diagram of a bilayer composite subjected to axial loading, (b) the corresponding boundary conditions where, ψ is the displacement potential function. Eq. (1) is valid for both plane stress and plane strain conditions.

The displacements and stresses can be represented in terms of the displacement potential function as follows [26]:

$$u = \frac{\partial^2 \psi}{\partial x \partial y} \quad (2)$$

$$v = -\frac{1}{1+\mu} \left[(1-\mu) \frac{\partial^2 \psi}{\partial y^2} + 2 \frac{\partial^2 \psi}{\partial x^2} \right] \quad (3)$$

$$\sigma_x = \frac{E}{(1+\mu)^2} \left[\frac{\partial^3 \psi}{\partial x^2 \partial y} - \mu \frac{\partial^3 \psi}{\partial y^3} \right] \quad (4)$$

$$\sigma_y = -\frac{E}{(1+\mu)^2} \left[\frac{\partial^3 \psi}{\partial y^3} + (2+\mu) \frac{\partial^3 \psi}{\partial x^2 \partial y} \right] \quad (5)$$

$$\sigma_{xy} = \frac{E}{(1+\mu)^2} \left[\mu \frac{\partial^3 \psi}{\partial x \partial y^2} - \frac{\partial^3 \psi}{\partial x^3} \right] \quad (6)$$

The Eqs. (2)–(6) are valid no matter the problem is plane stress or plane strain. The solution of the governing equation (Eq. (1)) would give the displacement potential function at every point in the material and then Eqs. (2)–(6) can be used for displacement and stress distributions in the material. However, no analytical solution exists for Eq. (1) under the prescribe boundary conditions in Fig. 1(b). Hence, we seek for a numerical method for an approximate solution to the problem. In this paper, we used a finite difference method to solve the problem.

2.2 Numerical Modeling

To apply the finite difference method the domain of the problem has been discretized into suitable mesh size. The discretization of the bilayer is illustrated in Fig. 2. A convergence study has been performed to obtain the optimum mesh size of the discretization. An additional imaginary boundary is needed around the physical boundary to properly apply the governing equations at all inner nodes of the material. The boundary conditions has been applied at the boundary. At each boundary node two conditions apply, for example, top traction-free boundary has $\sigma_n = 0, \sigma_t = 0$. The both conditions are satisfied at the boundary nodes but one is assigned for the physical nodes and another is applied for the imaginary nodes. Using the Taylor series expansion, the governing equation can be discretized and expressed as Eq. (7)

$$zk1\{\psi(i-2, j) + \psi(i+2, j)\} - zk2\{\psi(i-1, j) + \psi(i+1, j)\} - zk3\{\psi(i, j+1) + \psi(i, j-1)\} + zk4.\psi(i, j) + zk5\{\psi(i-1, j-1) + \psi(i-1, j+1) + \psi(i+1, j-1) + \psi(i+1, j+1) + \psi(i, j-2) + \psi(i, j+2)\} = 0 \quad (7)$$

Where, $zk1 = r^4, zk2 = 4(r^4 + r^2), zk3 = 4(1 + r^2), zk4 = (6r^4 + 8r^2 + 6), zk5 = 2r^2$.

The stencil representation of the governing equation is illustrated in Fig. 3(a). In similar manner, the displacement and traction boundary conditions can be expressed in discretized form. The discretized equations are derived in such a way that the stencil of each boundary condition is confined within the layer. A representative form of the displacement boundary equation at the interface of the bilayer is illustrated in Fig. 3(b). Note that the nodes associated with the interface pivot point for the top layer are staying within the top layer. Same happened for

the bottom layer. In this way, all the mixed boundary conditions has been specially treated at the interface as well as in the corner points.


The detail of the numerical treatment of the boundary conditions are discussed in ref. [27].

3. RESULTS AND DISCUSSION

The analytical expressions of the difference equations were formulated by using a computer numerical code (FORTRAN language). A system of linear algebraic equations was formed in terms of displacement potential functions ψ as an unknown at each nodal point. Then the system of equations was solved by using Gaussian elimination method. At first, the finite difference results were verified with FEM results. Then the FDM results to study the effect of the Poisson's ration on the interface stress distributions are discussed.

3.1 Model Verification with FEM

A similar bilayer composite model has been setup by using an FEM software package for a particular set of material properties in the top and bottom layer. The following boundary conditions were used for both FDM and FEM model for comparison. At the left side of the bilayer, $u_n = 0, u_t = 0$; at the right side $\bar{\sigma}_n = \sigma^{yo} = \sigma_1/E_1 = \sigma_2/E_2 = 1.5 \times 10^{-4}, \bar{\sigma}_t = 0.0$; at the top and bottom surfaces $\bar{\sigma}_n = 0.0, \bar{\sigma}_t = 0.0$, where, σ^{yo} is the dimensionless stress; σ_1, σ_2 are the applied stress, E_1, E_2 are the modulus of elasticity, $\mu_1=0.32, \mu_2=0.28$ are the Poisson's ratios of the upper and lower material, respectively.

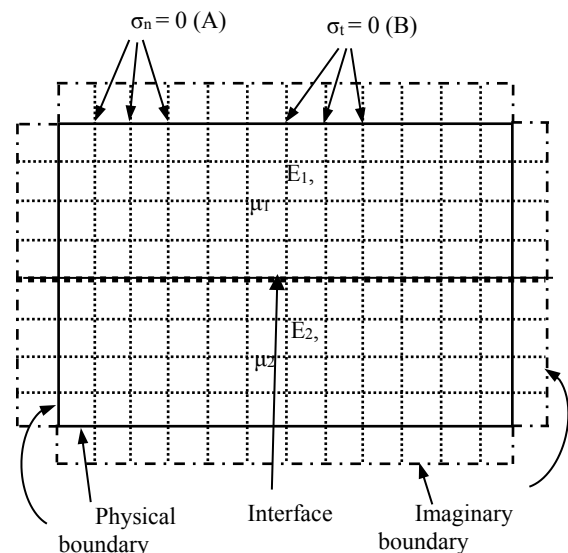

- A- satisfied at the inner physical boundary but assigned for imaginary nodes
- B- satisfied at the inner physical boundary but assigned for physical nodes

Fig. 2 Representative FDM discretization scheme: there are physical nodes and imaginary nodes outside the physical boundary. The boundary conditions are satisfied at the physical boundary but can be assigned for physical and imaginary nodes.

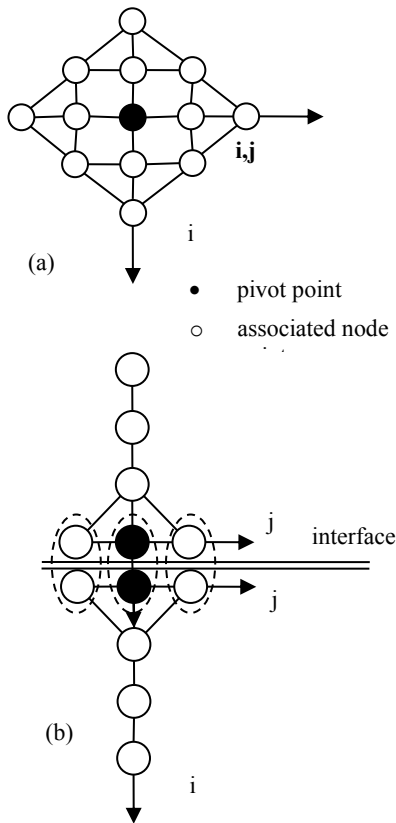


Fig. 3 Representative of the (a) stencil for the governing equations for the inner nodes of the material (b) stencil for the displacement component, u_x , at the interface of the bilayer composite.

A square geometry of the bilayer was considered for both cases having $a/b = 1.0$ and $a = b = 25$ unit. This problem is solved for stress and displacement distribution by using finite difference method and finite element method taking. The FDM results were found to be in good agreement with FEM results. The normalized normal stress (σ_y/E) distribution comparison is shown in Fig. 4(a) and (b) as a representative illustration. The stress components were chosen at (a) $y/b = 0.0$, (b) $y/b = 1$. Please note: for top layer, $E = E_1$, and for bottom layer, $E = E_2$. It was found that the FDM results were very good agreement with FEM results.

3.2 Effect of the Poisson's Ratios

A bilayer composite has a fixed boundary at the left side and is subjected to an uniform normalized normal stress $\bar{\sigma}_y = \sigma_1/E_1 = \sigma_2/E_2 = \sigma^{y0} = 1.5 \times 10^{-4}$ on the right side (in Fig. 1, $P = \bar{\sigma}_y$). Note that the stress component is normalized by the modulus of elasticity of respective layer. This form is very advantageous since we can apply the final results for any modulus of elasticity of interest. Also, note that the displacement and stress relation in Eq. (2)-(6) can easily be normalized by the modulus of elasticity. The top and bottom surfaces of the bilayer are traction-free. An FDM model was set up under the above-mentioned boundary conditions. Then the model was solved for different combinations of the Poisson's ratio of the two layers. Considering the practical applicability, the Poisson's ratio was varied for 0.2 to 0.4 since most of the materials have the Poisson's ratio in this range. For simplicity of demonstrating the

results, the Poisson's ratio variation in the bottom layer has been discussed here. The Poisson's ratio of the top layer was kept constant to $\mu_1 = 0.3$ which corresponds to the most common engineering material. In this paper, the results are presented in non-dimensional form. Hence, the results are generic and applicable to any geometry.

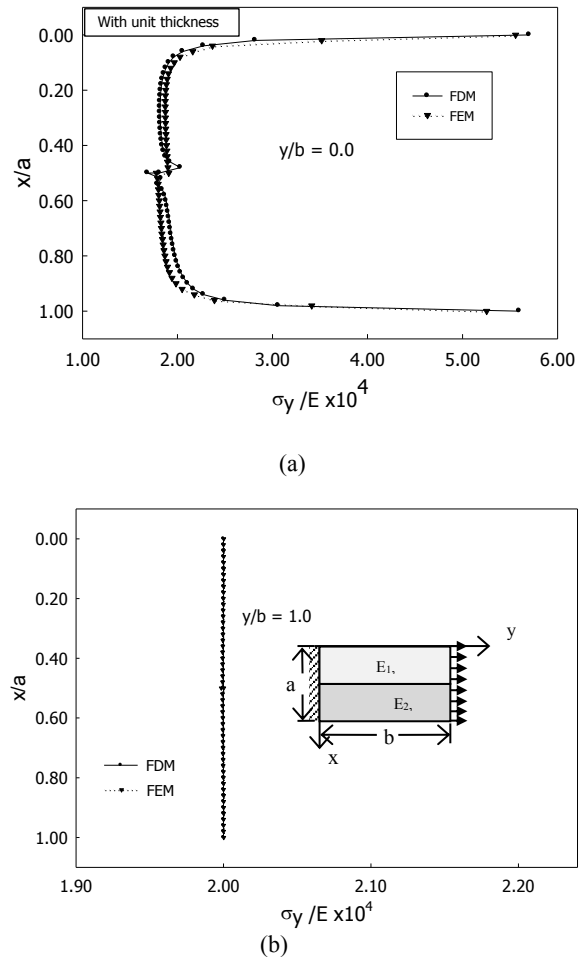


Fig. 4 Comparison between FEM vs FDM approach: normalized normal stress (σ_y/E) distribution at (a) $y/b = 0.0$, (b) $y/b = 1$. Please note: for top layer, $E = E_1$, and for bottom layer, $E = E_2$.

The variation of normalized displacement components, u/a and v/b for different Poisson's ratios is illustrated in Fig. 5(a) and (b). The geometric configuration of the bilayer is shown in an inset figure for better interpretation of the results. These results were extracted from a particular segment ($y/b = 0.24$) of the bilayer composite. It was found that the several of the Poisson's ratio in one layer affected the displacement distribution at another layer. The larger Poisson's ratio caused larger displacement component u in both layers. But for displacement component v had different trend in top and bottom layer. For displacement component v , the larger Poisson's ratio caused larger value in top layer but smaller value in bottom layer.

The normalized stress distributions are illustrated in Fig. 6, Fig. 7, and Fig. 8. The normal stress, σ_y and shear stress, σ_{xy} distributions are affected in both top and bottom layer although the Poisson's ratio of bottom layer was changed. But the normal stress, σ_x in the top layer was not affected much by the variation

of the Poisson's ratio of bottom layer. Also note that the shear stress, σ_{xy} at the top and bottom faces were found to be zero which verifies the applied traction-free boundary condition at the top and bottom.

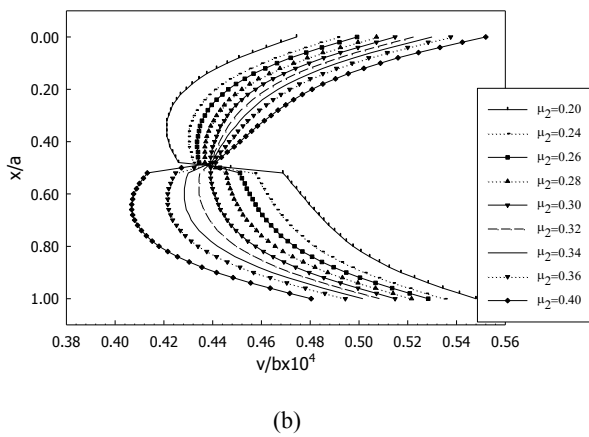
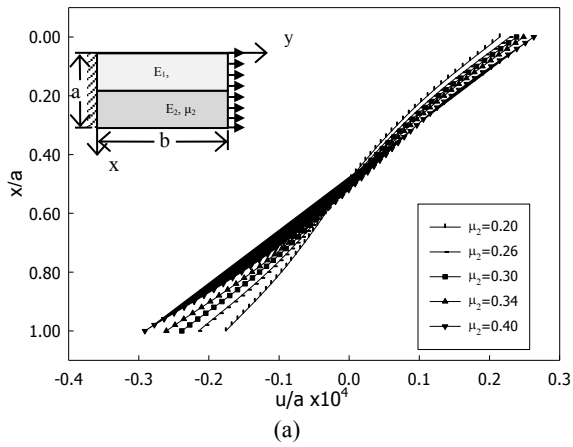


Fig. 5 (a) Variation of normalized displacement component (u/a) and (b) Variation of normalized displacement component (v/b) for different Poisson's ratios of lower material at y/b=0.24 of the bilayer composite.

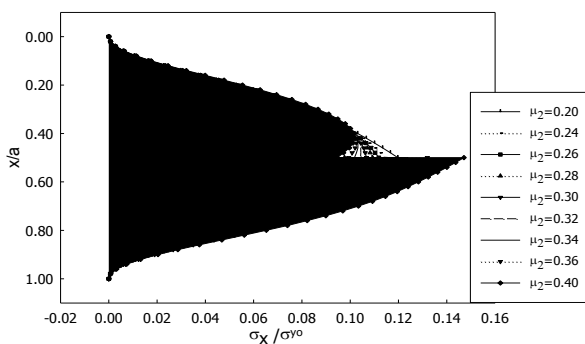


Fig. 6 Variation of normalized normal stress (σ_x / σ_y^0) for different Poisson's ratios of lower material at y/b=0.24 of the bilayer composite.

For all combinations of the Poisson's ratios the interface-stress state was affected. A jump in the normal stresses can be observed from the stress distribution plots in Fig. 6 and Fig. 7. But the normalized shear stress was found to be continuous over the interface of the bilayer composite. However, when the different modulus of elasticities would be inserted in the

normalized shear stress results there would be a jump in the actual shear stress.

In case of same materials at the top and bottom, the stress-jump would be diminished and become continuous stress distributions as expected.

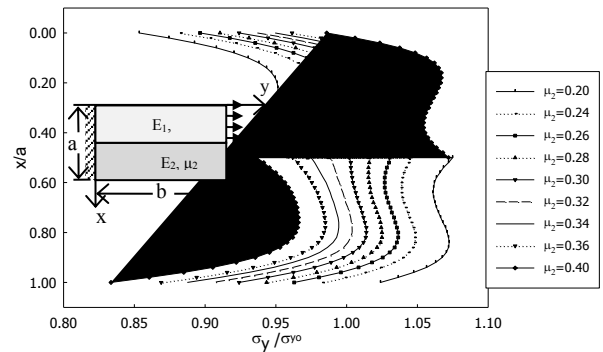


Fig. 7 Variation of normalized normal stress (σ_y / σ_y^0) for different Poisson's ratios of lower material at y/b=0.24 of the bilayer composite.

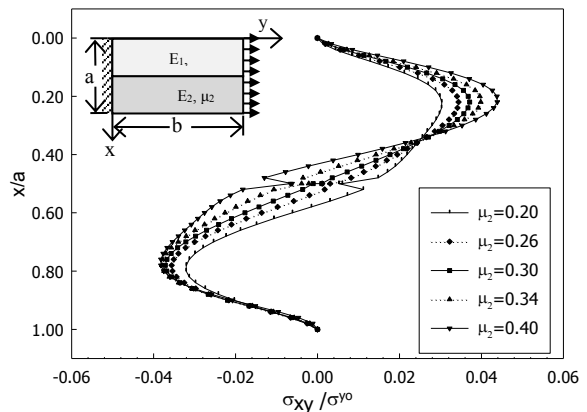


Fig. 8 Variation of normalized shear stress (σ_{xy} / σ_y^0) for different Poisson's ratios of lower material at y/b=0.24 of the bilayer composite.

4. CONCLUSION

The finite difference method (FDM) approach can accurately predict the displacement and stress state of a bilayer composite. The interfacial-stress state is highly affected by the different Poisson's ratios of the layers. Appropriate use of the difference equation is the key of the FDM solution for the composite layer. Proper treatment of the boundary conditions was performed at the interface and the corner points of the bilayer. It was found that the various of the Poisson's ratio in one layer affected the displacement and stress distribution at another layer. The larger Poisson's ratio caused larger displacement component u in both layers. But for displacement component v had different trend in top and bottom layer. Non-linear behavior and a sudden jump in the stresses was observed at the interface of the bilayer composite material.

6. ACKNOWLEDGEMENT

Support from the Directorate of Advisory, Extension and Research Services (DAERS) office, BUET is thankfully

acknowledged. The authors gratefully acknowledge the knowledgeable discussion with Dr. Shaikh Reaj Ahmed, Professor, Department of Mechanical Engineering, BUET.

REFERENCES

- [1] K. L. Reifsnider and A. Talug, "Analysis of fatigue damage in composite laminates", *International Journal of Fatigue*, Vol. 2, No. 1, pp. 3–11, 1980.
- [2] K. L. Reifsnider, K. Schulte and J. C. Duke, "Long-term fatigue behavior of composite materials", Philadelphia, PA, 1983.
- [3] V. Vadlamudi, R. Raihan and K. Reifsnider, "Multiphysics based simulation of damage progression in composites", *Materials Sciences and Applications*, Vol. 8, No. 5, pp. 389–404, 2017.
- [4] C. H. Woo, Y. C. Choi, J. S. Choi, H. Y. Lee and Y. W. Cho, "A bilayer composite composed of TiO₂-incorporated electrospun chitosan membrane and human extracellular matrix sheet as a wound dressing", *Journal of Biomaterials Science, Polymer Edition*, Vol. 26, No. 13, pp. 841–854, 2015.
- [5] K. Reifsnider, M. D. Rassel Raihan and V. Vadlamudi, "Heterogeneous fracture mechanics for multi-defect analysis", *Composite Structures*, Vol. 156, pp. 20–28, 2016.
- [6] P. K. Majumdar, M. Y. Bhuiyan, J. Clifford, F. H. Haider and K. L. Reifsnider, "Multi-physical description of material state change in composite materials", *Proceedings of the Society for the Advancement of Material and Process Engineering*, 2015, pp. 1–11.
- [7] A. Zubarev, "Investigation of monolayer-bilayer composite graphene structures", 2014 *International Semiconductor Conference (CAS)*, pp. 109–112, 2014.
- [8] Y. Zhang, "Interface layer effect on the stress distribution of a wafer-bonded bilayer structure", *Journal of Materials Science*, Vol. 43, No. 1, pp. 88–97, 2008.
- [9] S. Wang, C. M. Harvey, B. Wang and A. Watson, "Post-local buckling-driven delamination in bilayer composite beams", *Composite Structures*, Vol. 133, pp. 1058–1066, 2015.
- [10] Y. Boonyongmaneerat and C. A. Schuh, "Contributions to the interfacial adhesion in co-sintered bilayers", *Metallurgical and Materials Transactions A*, Vol. 37, No. 5, pp. 1435–1442, 2006.
- [11] C. M. Harvey, J. D. Wood, S. Wang and A. Watson, "A novel method for the partition of mixed-mode fractures in 2D elastic laminated unidirectional composite beams," *Composite Structures*, Vol. 116, pp. 589–594, 2014.
- [12] K. Zhang, L. Li, Y. Duan and Y. Li, "Experimental and theoretical stress analysis for an interface stress model of single-L adhesive joints between CFRP and aluminum components", *International Journal of Adhesion and Adhesives*, Vol. 50, pp. 37–44, 2014.
- [13] M. Y. Bhuiyan and V. Giurgiutiu, "Using the gauge condition to simplify the elastodynamic analysis of guided wave propagation", *Incas Bulletin*, Vol. 8, No. 3, pp. 11–26, 2016.
- [14] A. K. Ghosh and S. R. Ahmed, "Stress distribution at the stiffened edges of a thick curved flat bar", *Procedia Engineering*, Vol. 90, pp. 219–224, 2014.
- [15] M. K. H. Pulo, "Stress analysis of a sandwich structure having isotropic layers using finite difference method", *Bangladesh University of Engineering and Technology*, 2016.
- [16] S. R. Ahmed, A. B. M. Idris and M. W. Uddin, "Numerical solution of both ends fixed deep beams", *Computers & Structures*, Vol. 61, No. 1, pp. 21–29, 1996.
- [17] J. O. Dow, M. S. Jones and S. A. Harwood, "A new approach to boundary modelling for finite difference applications in solid mechanics", *International Journal for Numerical Methods in Engineering*, Vol. 30, No. 1, pp. 99–113, 1990.
- [18] M. Z. Hossain, S. R. Ahmed and M. W. Uddin, "Generalized mathematical model for the solution of mixed-boundary-value elastic problems", *Applied Mathematics and Computation*, Vol. 169, No. 2, pp. 1247–1275, 2005.
- [19] M. M. Hassan, "Effect of Poisson's ratio on material properties characterization by nanoindentation with a cylindrical flat tip indenter", *South Dakota State University*, 2016.
- [20] S. K. D. Nath and C. H. Wong, "Finite-difference solution of a both-end-fixed orthotropic composite beam under uniformly distributed loading using displacement potential function formulation", *Journal of Engineering Mechanics*, Vol. 137, No. 4, pp. 258–267, 2011.
- [21] S. Timoshenko and V. N. Goodier, *Theory of Elasticity*, 3rd ed. McGraw-Hill Book Company, New York, 1979.
- [22] M. A. S. Akanda, S. R. Ahmed and M. W. Uddin, "Stress analysis of gear teeth using displacement potential function and finite differences", *International Journal for Numerical Methods in Engineering*, Vol. 53, No. 7, pp. 1629–1640, 2002.
- [23] M. A. S. Akanda, S. R. Ahmed, M. R. Khan, and M. W. Uddin, "A finite-difference scheme for mixed boundary value problems of arbitrary-shaped elastic bodies", *Advances in Engineering Software*, Vol. 31, No. 3, pp. 173–184, 2000.
- [24] S. R. Ahmed, M. Z. Hossain, and M. W. Uddin, "A general mathematical formulation for finite-difference solution of mixed-boundary-value problems of anisotropic materials", *Computers & Structures*, Vol. 83, No. 1, pp. 35–51, 2005.
- [25] S. R. Ahmed, M. R. Khan, K. M. S. Islam and M. W. Uddin, "Investigation of stresses at the fixed end of deep cantilever beams", *Computers & Structures*, Vol. 69, No. 3, pp. 329–338, 1998.
- [26] M. W. Uddin, "Solution of two-dimensional elastic problems with mixed boundary conditions", *Carleton University, Canada*, 1966.
- [27] M. Y. Bhuiyan, "Interface stress analysis of two bonded isotropic materials by finite difference method", *Bangladesh University of Engineering and Technology*, 2013.